

AD



AD 651194


TECHNICAL REPORT ECOM-02205-3

INVESTIGATION OF MECHANISMS FOR ELECTROCHEMICAL CATALYSIS

THIRD QUARTERLY REPORT

By

J. R. Aylward—S. W. Smith

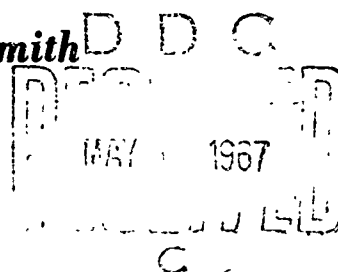

MAY 1967

DISTRIBUTION OF THIS REPORT IS UNLIMITED

ECOM

UNITED STATES ARMY ELECTRONICS COMMAND • FORT MONMOUTH, N.J.

CONTRACT DA 28-043 AMC-02205(E)

UNITED AIRCRAFT CORPORATION

PRATT & WHITNEY AIRCRAFT DIVISION

East Hartford, Connecticut

ARCHIVE COPY

Technical Report ECOM-02205-3

May 1967

INVESTIGATION OF MECHANISMS FOR
ELECTROCHEMICAL CATALYSIS

Quarterly Report
November 1, 1966 to January 31, 1967
Report No. 3

Contract No. DA-28-043-AMC-02205(E)
DA Project No. 1CO14501A34A00, Task 11

Prepared by

J. R. Ayiward and S. W. Smith
United Aircraft Corporation
Pratt & Whitney Aircraft Division
East Hartford, Connecticut

for

U. S. Army Electronics Command
Fort Monmouth, New Jersey

Distribution of This Document is Unlimited

PRATT & WHITNEY AIRCRAFT

FOREWORD

This report was produced in accordance with U. S. Army Contract No. DA-28-043-AMC-02205(E) by the Pratt & Whitney Aircraft Division of the United Aircraft Corporation. It discusses the work performed during the period from November 1, 1966, through January 31, 1967.

ABSTRACT

A program is being conducted to investigate the mechanisms of electrocatalysis with respect to the anodic oxidation of selected fuels by novel electrocatalysts in acid electrolyte at temperatures below 150°C and at ambient pressure. Major emphasis has been given to the investigation of the properties of transition metal silicides when surface-doped with platinum, gold, or both.

Conflicts had occurred in the data for silicides incorporated on gold and gold-plated current collectors, but investigation during the current quarter indicates that the conflicts resulted from platinum contamination. The study also showed that TiSi_2 exhibits some activity for hydrogen and methanol oxidation.

The electrochemical behavior of WSi_2 in acid electrolyte was studied and was found to be similar to that of MoSi_2 . Both of these materials have tetragonal structures. VSi_2 and TaSi_2 also have similar electrochemical characteristics, and both have hexagonal structures.

Experiments with platinum-doped TiSi_2 electrodes indicates that relatively large amounts of platinum are required to obtain a catalytic activity which approaches that of an equivalent platinum sheet and that the utilization of the platinum is low. However, gold-platinum co-deposits on TiSi_2 exhibit markedly different behavior. The current obtained from the co-deposits as the ratio of gold to platinum was varied shows maxima at 50 and 70 weight percent of gold and a sharp minimum at 55 weight percent of gold. The maxima are higher than the levels of activity obtained with platinum alone.

TABLE OF CONTENTS

	<u>Page</u>
FOREWORD	ii
ABSTRACT	iii
LIST OF FIGURES	v
I. INTRODUCTION	1
II. PROGRESS	2
A. Catalytic Activity of TiSi_2	2
B. Preliminary Data for WSi_2	5
C. Electrochemical Behavior of the Silicides	7
1. Effect of Crystal Structure on Electrochemical Behavior	7
2. Investigation of Cathodic Current of TaSi_2 at 100 mv	9
D. Noble Metal Utilization on TiSi_2	10
E. Effect of Gold-Platinum Ratio on TiSi_2 Surface Doping	13
III. CONCLUSIONS AND RECOMMENDATIONS	15

LIST OF FIGURES

<u>Number</u>	<u>Title</u>	<u>Page</u>
1	Activity of Gold Sheet Current Collector With an Without TiSi_2 Powder for Hydrogen Oxidation When a Platinum Counter Electrode is Employed	3
2	Triangular Potential Sweep Curves for WSi_2 With Sweep Rate of 34 mv/sec	5
3	Triangular Potential Sweep Curves for WSi_2 With Sweep Rate of 100 mv/min	6
4	Steady-State Current-Voltage Characteristic for WSi_2	6
5	Crystal Structure of Silicides	7
6	Steady-State Current-Voltage Characteristics for WSi_2 and MoSi_2	8
7	Steady-State Current-Voltage Characteristics for TaSi_2 and VSi_2	8
8	Steady-State Current-Voltage Characteristics for TiSi_2	9
9	Effect of Prepolarization at +1200 mv and -1200 mv on the Cathodic Current of TaSi_2 at 100 mv	10
10	Anodic Branches of Triangular Potential Sweep Curves for Smooth and Platinized (Platinum) Rotating Disk Electrodes With Sweep Rate of 34 mv/sec	11
11	Anodic Branches of Triangular Potential Sweep Curves for Smooth and Platinized (Platinum) Flag-Type Electrodes With Sweep Rate of 34 mv/sec	11
12	Activity for Hydrogen Oxidation of Platinum-Gold Co-deposit Relative to that of Platinum	14

I. INTRODUCTION

A program is being conducted to investigate the mechanism of electrocatalysis with respect to the anodic oxidation of selected fuels by novel electrocatalysts in acid electrolyte at temperatures below 150°C and at ambient pressure. The studies are particularly concerned with the influence of surface properties on catalytic activity. The study is being conducted in an effort to identify active, low-cost catalysts for direct-energy conversion devices such as fuel cells.

The work performed during this report period involved study of the electrochemical behavior of selected transition-metal silicides and the effect on this behavior of adding trace amounts of gold and platinum to the surfaces of the silicides.

II. PROGRESS

A. CATALYTIC ACTIVITY OF TiSi_2

During the first quarterly period, TiSi_2 was found to have some catalytic activity when it was incorporated on a gold-plated platinum-sheet current collector. However, when a pure gold-sheet current collector was used, no activity could be detected. In both cases, a gold counter electrode was used. The understanding of this behavior was further complicated by data obtained prior to the current contract which indicated that certain silicides have considerable activity for hydrogen and methanol oxidation, whereas activity of the magnitude indicated by this data has not been duplicated during the current studies. Since the previous tests were performed with a platinum counter electrode, it was suspected that the high activity sometimes observed was caused by platinum contamination. Testing during this report period was directed toward verifying this hypothesis.

Testing was conducted in the original cell shown in Figure 1 of the first quarterly report. A pure gold sheet was used for the counter electrode and three different materials were used for current collectors, namely, platinum, gold-plated platinum, and gold. The electrolyte used was 1-molar H_2SO_4 at 50°C , with hydrogen and methanol as fuels. For each test point, the potential was maintained constant for ten minutes before current readings were taken to provide essentially steady-state data.

Initially, the activity of the current collectors was measured to obtain baseline data. Subsequently, the TiSi_2 , mixed with 15 weight percent Teflon powder for binding, was pressed onto the current collectors and sintered at 250°C for five minutes. The current for hydrogen oxidation at a potential of 200 mv was then measured, and the results are shown in Table I.

TABLE I

Activity of TiSi_2 for Hydrogen Oxidation on Various
Current Collectors

Current-Collector Material	Current for Hydrogen Oxidation at 200 mv (ma)	
	Current Collector Only	TiSi_2 on Current Collector
Platinum	1.2	0.3
Gold-Plated Platinum	0.3	0.2
Gold	0.05	0.12

Note: Corrosion current for TiSi_2 (nitrogen gas) at 200 mv was 0.005 ma.

As shown, the TiSi_2 on the platinum and the gold-plated platinum current collectors actually inhibited rather than increased the catalytic activity. On the gold current collector, however, the TiSi_2 increased the current over that of the gold current collector alone. Hence, it appears that TiSi_2 powder does have some activity for hydrogen oxidation. The higher currents obtained with the other electrodes are probably a combination of the current from the TiSi_2 and from the exposed platinum.

These results were then related to the tests performed prior to the current contract by testing the gold current collector with a platinum counter electrode. Further, to conform to the procedure used in the previous tests, a corrosion test using a nitrogen-saturated electrolyte was conducted before the oxidation tests were conducted. This was done to determine if the procedure allowed platinum to dissolve from the counter electrode and then diffuse over to and plate onto the working electrode. As for the previous tests, each potential was maintained for ten minutes before current readings were recorded. The electrolyte concentration and temperature were the same as used previously. The results obtained for the current collector alone and for the current collector with TiSi_2 powder are shown in Figure 1. These results show beyond any doubt that the gold sheet was contaminated with platinum from the platinum counter electrode, since considerable current was obtained with the current collector alone, and pure gold has no activity for hydrogen oxidation. The higher limiting current obtained with the TiSi_2 powder is attributed to the larger surface area produced by the powder. The limiting current obtained is approximately the same as that obtained prior to the contract for TiSi_2 .

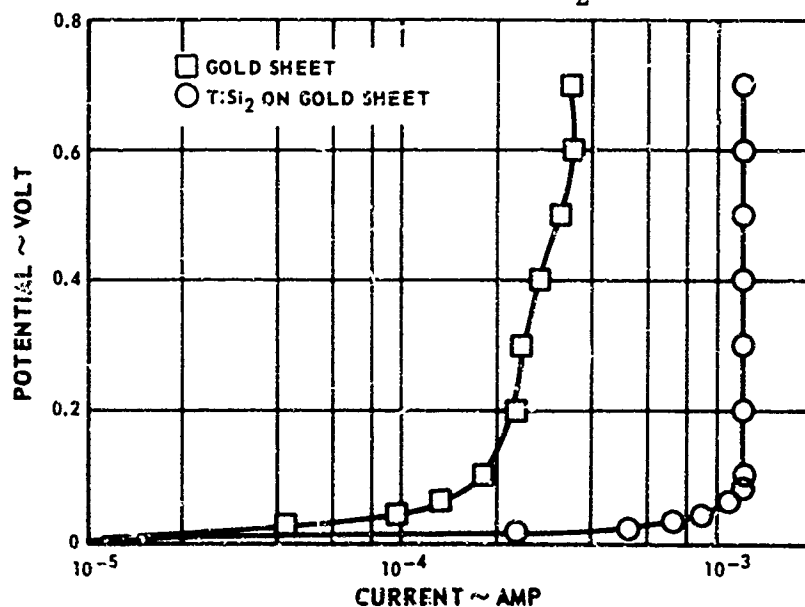


Figure 1 Activity of Gold Current Collector With and Without TiSi_2 Powder for Hydrogen Oxidation When a Platinum Counter Electrode is Employed

Additional tests were performed for a gold-sheet working electrode and for TiSi_2 supported on the gold sheet in the cell shown in Figure 1 of the second quarterly report. A gold counter electrode was used for these tests to avoid platinum contamination. The working electrode used in this cell was a rotating sheet, and the TiSi_2 was mixed with 15 weight percent Teflon 30 and water and then sprayed onto the sheet. after which it was sintered at 250°C for five minutes. The same electrolyte concentration and temperature were used as for previous tests. When nitrogen or hydrogen gases were used, they were bubbled through the electrolyte in the working electrode compartment. Methanol fuel was used at a concentration of 0.1 molar.

The test results obtained are shown in Table II. As shown, the currents at 600 mv for both hydrogen and methanol oxidation with TiSi_2 are considerably higher than those obtained with the gold sheet, and these currents are significantly higher than the corrosion current of the TiSi_2 .

TABLE II

Activity of TiSi_2 on Rotating Flag-Type Gold Current
Collector for Hydrogen and Methanol Oxidation
at a Potential of 600 mv

<u>Electrode Material</u>	<u>Current for Nitrogen (μa)</u>	<u>Current for Hydrogen (μa)</u>	<u>Current for Methanol (μa)</u>
Gold Sheet	-	< 1	1.1
TiSi_2 on Gold Sheet	2	16	4.3

From the data obtained during this quarter, it can be concluded that TiSi_2 powder has some catalytic activity for hydrogen and methanol oxidation. Previous tests on sintered plugs of TiSi_2 detected no catalytic activity, but this is not surprising since the high temperatures used in sintering the powder would undoubtedly destroy the active sites.

The relatively high activity found previously for the silicides was apparently caused by platinum contamination from the counter electrode. The effect of the contamination differed among the silicides because some silicides are more amenable to platinum activation than others.

B. PRELIMINARY DATA FOR WSi_2

The electrochemical behavior of WSi_2 was investigated by the same procedure and at the same conditions used to study the silicides of titanium, molybdenum, vanadium, and tantalum. The potential sweep and steady-state (taken after maintaining the potential constant for 15 minutes) data for WSi_2 is shown in Figures 2, 3, and 4. As shown, there is essentially no difference between the curves obtained with solutions saturated with argon and those saturated with hydrogen. Further, the corrosion currents are approximately ten times those obtained with the titanium and molybdenum disilicides.

Subsequently, $2.8 \mu\text{g}$ of platinum was added to the WSi_2 electrode by adding the platinum to the solution and holding the electrode at -600 mV for 30 minutes. Triangular potential sweeps were made between -600 mV and 1100 mV at rates of 34 mV/sec and 100 mV/sec . As in the case of MoSi_2 , the overvoltage in the hydrogen evolution region was reduced, but no activity for the oxidation of hydrogen could be observed. The magnitude of the corrosion current was not reduced significantly by the addition of platinum. No attempt has been made to activate the electrodes by depositing the platinum over a gold deposit.

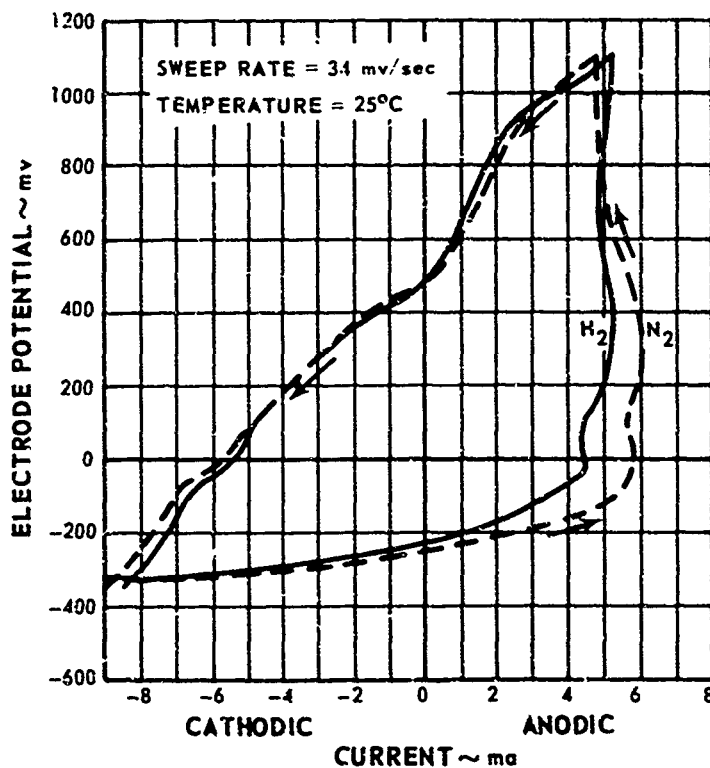


Figure 2 Triangular Potential Sweep Curves for WSi_2 With Sweep Rate of 34 mV/sec

PRATT & WHITNEY AIRCRAFT

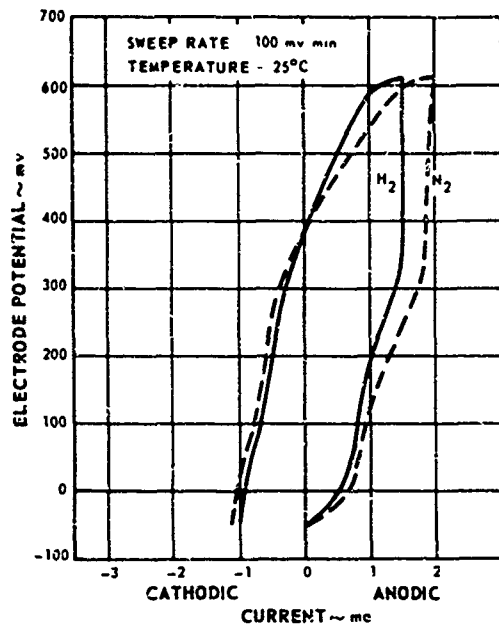


Figure 3 Triangular Potential Sweep Curves for WSi₂ With Sweep Rate of 100 mv/min

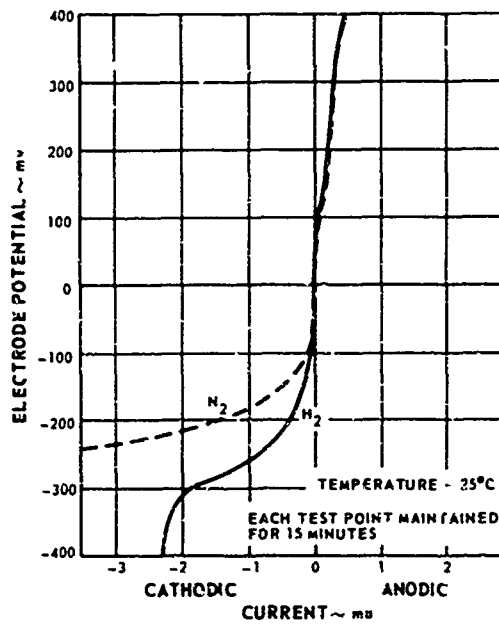


Figure 4 Steady-State Current-Voltage Characteristic for WSi₂

C. ELECTROCHEMICAL BEHAVIOR OF THE SILICIDES

Two studies were conducted to investigate the electrochemical behavior of the silicides in the absence of fuel. The first of these involved a correlation of crystal structure with behavior, and the second involved an experiment to determine the cause of the cathodic current observed at low positive potentials for TaSi₂ and VSi₂.

1. Effect of Crystal Structure on Electrochemical Behavior

During the course of the program, the electrochemical behavior of TaSi₂ was found to be similar to that of VSi₂, but quite different from that of TiSi₂ or MoSi₂. Since the structures of TaSi₂ and VSi₂ are the same, it was postulated that the similarity in electrochemical behavior was related to the crystal structure. Both VSi₂ and TaSi₂ have hexagonal structures; MoSi₂ and WSi₂ have tetragonal structures, and TiSi₂ has an orthorhombic structure. TiSi₂ is built of close-packed layers of the type shown in Figure 5. The titanium atoms of successive layers fall above the points B, C, and D, respectively. Therefore, each atom has ten neighbors. Each titanium atom is approximately equidistant from ten silicon atoms, and each silicon atom is approximately equidistant from five titanium atoms and five silicon atoms. In the VSi₂ and TaSi₂ hexagonal structures, the repeating unit is comprised of only three layers instead of four, with the metal atoms of successive layers falling above the points B and D only. In the tetragonal structures of MoSi₂ and WSi₂, however, the repeating unit is comprised of only two layers, with the adjacent layers being displaced with respect to one another such that the metal atom of one layer falls above point B of the other. Consequently, the three structures form an interesting series, all being built from the same type of close-packed layer superimposed in the same way so that each atom has ten neighbors, but differing in the number of layers in the repeating unit.

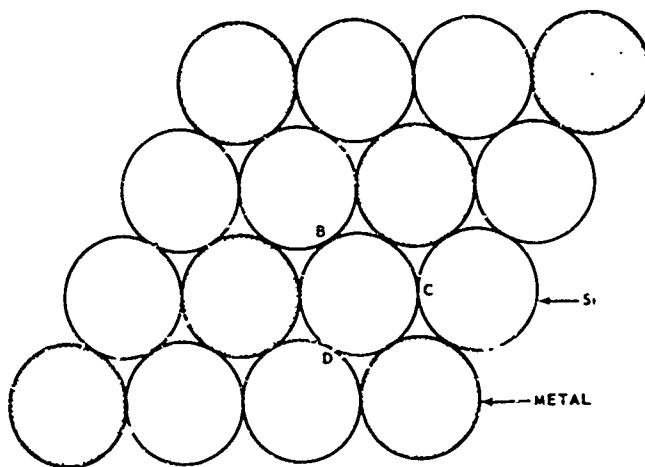


Figure 5 Crystal Structure of Silicides

From this analysis, it was concluded that the electrochemical behavior of WSi_2 should be similar to that of MoSi_2 , the behavior of TaSi_2 should be similar to that of VSi_2 , and the behavior of TiSi_2 should be different from that of either of the other two types of silicides. This is shown to be the case in the steady-state curves shown in Figures 6, 7, and 8. (These data were obtained by recording current readings after the corresponding potential had been maintained for ten minutes in a nitrogen-saturated electrolyte.)

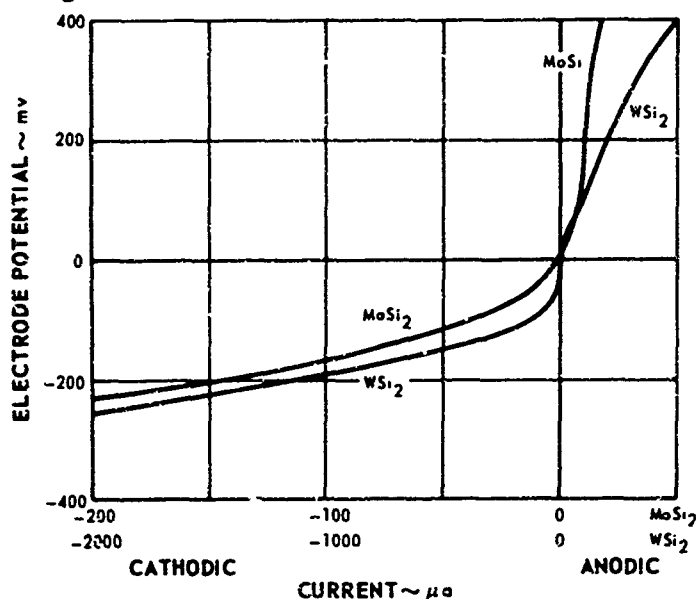


Figure 6 Steady-State Current-Voltage Characteristics for WSi_2 and MoSi_2

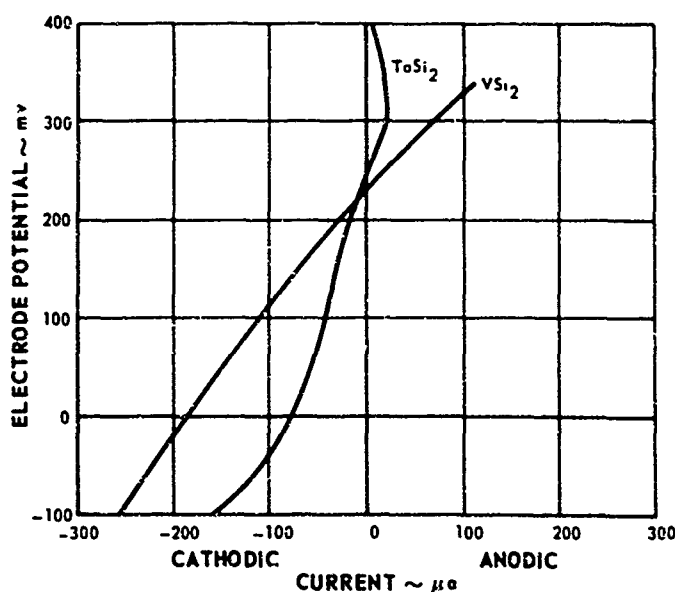


Figure 7 Steady-State Current-Voltage Characteristics for TaSi_2 and VSi_2

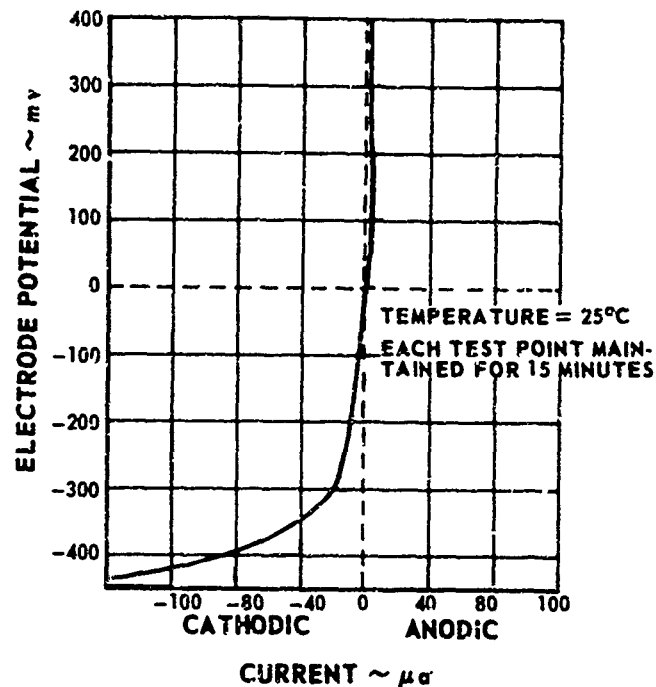


Figure 8 Steady-State Current-Voltage Characteristics for TiSi_2

2. Investigation of Cathodic Current of TaSi_2 at 100 mv

Both TaSi_2 and VSi_2 are characterized by cathodic current at potentials below 200 mv, and it was not known whether this current is caused by impurities or by the reduction of the oxide film. To find out, a rotating sintered TaSi_2 electrode was treated in 1-molar H_2SO_4 electrolyte at 25°C by maintaining a potential of 1200 mv for one hour. The cathodic current was then measured as a function of time at 100 mv. The electrode was then held at -1200 mv for one hour, after which the current was again recorded at 100 mv.

The results of the two tests are shown in Figure 9. As shown, pretreatment at 1200 mv was followed by an initial cathodic current of 1.3 ma at 100 mv which decayed relatively steadily and was still progressing after ten hours, when the test was terminated. This behavior is attributed to the reduction of the oxide formed at the more positive potential. After pretreatment at -1200 mv, the cathodic current remained constant at 0.22 ma. This behavior is difficult to explain in terms of oxide film formation, known reactions, or impurities and is not understood at this time.

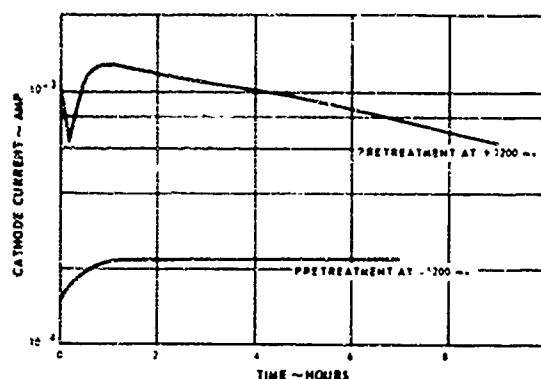


Figure 9 Effect of Prepolarization at +1200 mv and -1200 mv on the Cathodic Current of TaSi₂ at 100 mv

D. NOBLE METAL UTILIZATION ON TiSi₂

A series of experiments were performed to find a more quantitative measure of noble metal utilization on a silicide surface and to provide a baseline for judging the activity of surface-doped electrodes. The activity for hydrogen oxidation of smooth and platinized platinum electrodes of both the rotating flag and disk type was measured at the same conditions used for the silicide. Sweep curves were generated with a sweep rate of 34 mv/sec, and the results are shown in Figures 10 and 11. True surface area was determined by measuring the double-layer capacitance (assuming that smooth platinum has a double-layer capacitance of 40 $\mu\text{F}/\text{cm}^2$ true area) and by determining the hydrogen adsorption. The capacitance is determined from the curves by relating the current in the double-layer region to the voltage sweep rate. Hydrogen adsorption was determined by integrating the area under the sweep curve in the hydrogen adsorption region. The amount of charge involved for a theoretically smooth surface was calculated on the basis of the assumption that one atom of hydrogen is adsorbed on each surface platinum atom. The results of the area measurements normalized with respect to geometric area are shown in Table III.

TABLE III

Electrochemical Parameters for Rotating Disk and Flag-Type Platinum Electrodes

Electrode	Measured Double-Layer Capacitance ($\mu\text{F}/\text{cm}^2$)	Measured Hydrogen Adsorption ($\mu\text{ coul}/\text{cm}^2$)	Calculated Hydrogen Adsorption ($\mu\text{ coul}/\text{cm}^2$)	Surface Roughness (Real Area/Geometric Area)	
				Double-Layer Capacitance	Hydrogen Adsorption
Disk (Smooth)	60	235	185	1.5	1.4
Flag (Smooth)	34	294	185	1.4	1.6
Disk (Black)	965	-	-	24	-
Flag (Black)	2500	10,600	185	62	57

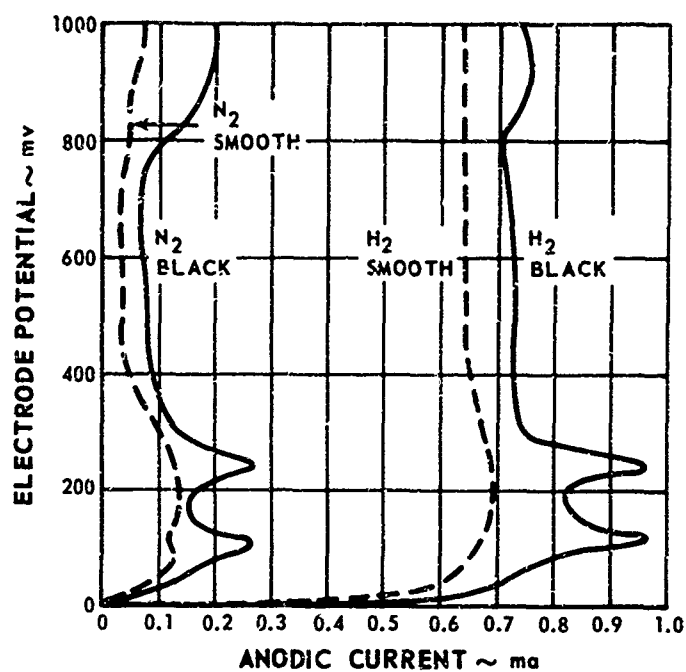


Figure 10 Anodic Branches of Triangular Potential Sweep Curves for Smooth and Platinized (Platinum) Rotating Disk Electrodes With Sweep Rate of 34 mv/sec

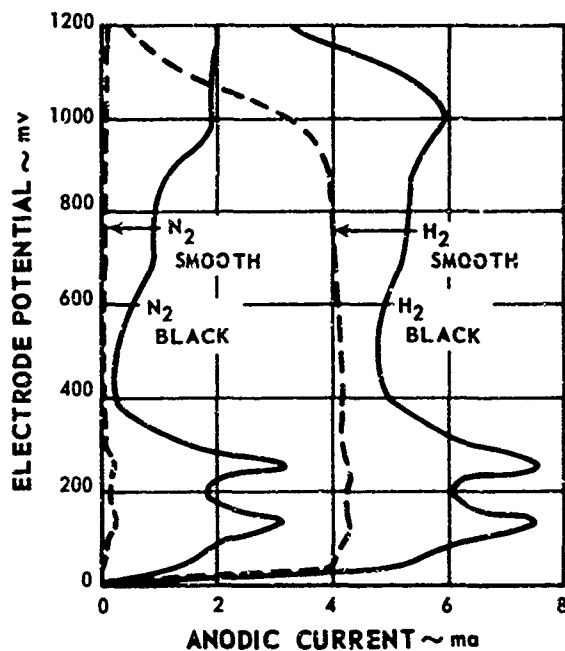


Figure 11 Anodic Branches of Triangular Potential Sweep Curves for Smooth and Platinized (Platinum) Flag-Type Electrodes With Sweep Rate of 34 mv/sec

The sweep curves (Figures 10 and 11) show that, in the case of hydrogen, the current in the limiting current region is not a function of the surface roughness, at least for a factor of 40 change in the roughness factor. This is to be expected in a mass-transport controlled process. Comparison of the limiting currents obtained with the disk and with the flag-type electrode reveals that the disk provides a higher limiting current by a factor of 1.5 for equivalent true areas.

From the limiting current on the rotating disk and from the fact that the current is limited by the geometry of the system, the amount of current which would be obtained from a geometrically flat monolayer of platinum having the dimensions of the disk can be calculated. This would represent complete utilization of the platinum for this system. For this calculation, it was assumed that the platinum forms in a square array for the first monolayer with an atomic radius equivalent to that calculated from the density. On this basis, a monolayer of platinum with an area of one square centimeter is equivalent to 0.36 μg , and, consequently, for the electrode disk size used, 0.12 μg would be required to form a monolayer over the disk surface, providing the surface is flat. Hence, if at least 0.12 μg of platinum is deposited as a monolayer on the surface of the silicide electrode, the limiting current should be 0.64 ma.

Comparison of this conclusion with the experimental results for platinum and platinum on gold deposited on TiSi_2 (see Figure 7 of the second quarterly report) does not verify the theory, however. Although the amount of platinum applied to the silicide exceeded the amount required to produce a monolayer over the geometrical surface area by a factor of about 10, the limiting current was 0.55 rather than 0.64 ma. This indicates that the utilization of the platinum is low, and, consequently, it is clear that it is not deposited in a monolayer, but rather in discrete islands. This would result in a simple geometrical area effect, reducing the diffusion current by the ratio of the area covered with platinum to the total area. In addition to this effect, the silicides have a relatively rough surface, which requires a larger amount of platinum to completely cover the surface. Hence, the lower limiting current for the silicide electrodes and the relatively large amount of platinum required seems to result from the combination of two factors which are inseparable until either the true surface area or the deposit crystallite size (or, complementarily, the fraction of the substrate covered) is measured.

An attempt was made to measure the surface roughness of the TiSi_2 electrode by plating it with gold, since the double-layer capacitance of the resulting surface could be compared with that of a smooth gold sheet to calculate the relative surface area. The TiSi_2 electrode was cleaned by immersion in a HNO_3 -HF mixture at 90°C for one minute followed by rinsing in distilled water. It was then placed for two minutes in a solution containing 1 g $\text{KAu}(\text{CN})_2$, 2 ml 48 percent HF, and 100 ml H_2O , at room temperature. A shiny gold plate resulted. How-

ever, it was not possible to measure the double-layer capacity of the plated plug because the electrochemical behavior was the same as that of the unplated silicide. Apparently, the TiSi_2 plug is porous enough that the electrolyte penetrates into the structure.

E. EFFECT OF GOLD-PLATINUM RATIO ON TiSi_2 SURFACE DOPING

A series of experiments were reported in the second quarterly report in which TiSi_2 was plated from a sulfuric acid solution containing equal molar amounts of gold and platinum. The results were unusual since the sweep curve showed no defined limiting current and the maximum currents obtained were about 40 percent higher than the limiting current obtained for the rotating platinum disk.

During this report period, similar experiments were performed with co-deposits of platinum and gold, but the amount of platinum was held constant at $0.2 \mu\text{g}$ and the amount of gold was varied. The ratio of the current obtained for the co-deposit to that obtained for platinum is plotted in Figure 12 as a function of the weight percent of gold in the deposit. The curve exhibits maxima at 50 and 70 percent of gold which are higher than the level obtained with $0.2 \mu\text{g}$ of platinum alone. A sharp minimum occurs at about 55 percent of gold. There is some uncertainty in the absolute values of these percentages because of the small amount of the materials involved and because of the sharpness of the maxima and the minimum. However, a sufficient number of points have been repeated to assure that the general shape of the curve is correct and that the minimum occurs close to the indicated value. It is difficult to interpret these results because the character of the surface is not known, that is, it is not known whether the deposit is a mixture or an alloy. At present, an attempt is being made to correlate the results with those published by M. W. Breiter* on hydrogen adsorption on heterogeneous platinum-gold alloys.

* M. W. Breiter, Transactions of the Faraday Society, Vol. 61, p. 749, 1965

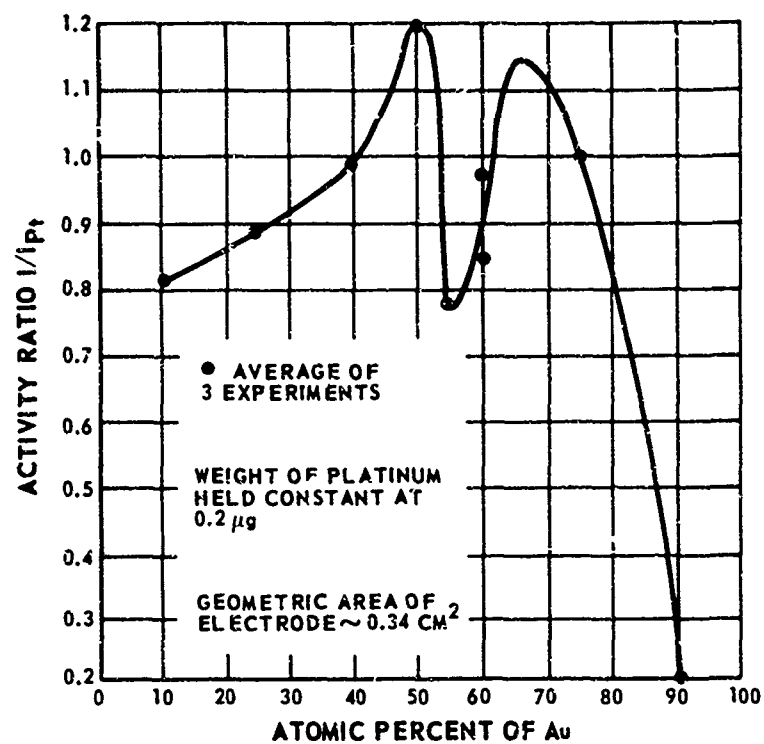


Figure 12 Activity for Hydrogen Oxidation of Platinum-Gold Co-deposit Relative to that of Platinum

III. CONCLUSIONS AND RECOMMENDATIONS

The experiments performed on TiSi_2 on a gold substrate indicate that TiSi_2 powder has a slight catalytic activity for hydrogen and methanol oxidation, whereas TiSi_2 in the form of a sintered plug has no detectable catalytic activity. This is not surprising since the high temperatures used during fabrication of the plug could destroy the active sites. The activity previously reported for the silicides on a gold-plated platinum current collector is probably caused largely by the small amount of exposed platinum on the current collector rather than by the silicide. Further, since corrosion testing was usually performed first, some of the exposed platinum could dissolve in the electrolyte at the high potentials used and subsequently plate out on the silicide at lower potentials. The higher catalytic activity observed during testing conducted prior to the contract apparently was caused by plating of the silicide with platinum from the platinum counter electrode used at that time.

The electrochemical behavior of the silicides in the absence of fuel was found to be related to crystal structure. VSi_2 and TaSi_2 have hexagonal structures and similar electrochemical characteristics. Similarly, WSi_2 and MoSi_2 both have tetragonal structures and also have similar electrochemical characteristics, but different characteristics from those of VSi_2 and TaSi_2 .

Surface doping of TiSi_2 with platinum and with platinum-gold combinations by electrodeposition from very dilute solutions of gold in sulfuric acid results in low utilization of the noble metal. No evidence was found that the silicide made any significant contribution to the catalytic activity observed under these conditions. Since no catalytic activity on the part of the silicides has been observed, it is recommended that further studies of silicides be abandoned. The use of silicides solely as catalyst supports does not appear to be desirable because of the difficulty in obtaining silicides in a finely divided state and because, in the finely divided state, they have a high electronic resistance because of the high ratio of oxide volume to silicide volume.

Tests have indicated that platinum contamination of the current collector can seriously distort the results. The amount of platinum responsible for the activity observed on gold in Figure 1 is not known, but it must be present in very small amounts. Consequently, some of the data published in the literature on electrodes other than platinum is questionable, since most workers have used platinum as a counter electrode. An even more serious source of platinum contamination would be the fairly standard practice of conducting pre-electrolysis of the electrolyte using platinum electrodes. The resulting contamination of the electrolyte with platinum and its subsequent deposition on the electrode under study could seriously affect the results.

PRATT & WHITNEY AIRCRAFT

Because the platinum contamination is of considerable significance to the study of electrocatalysis and since the silicides have been found to be unsuitable as catalysts for hydrogen or methanol reduction, it is recommended that the remainder of the contract effort be devoted to the study of the effect of trace amounts of platinum on a gold substrate. It would be of interest to determine how small an amount of platinum can be detected on gold by electrochemical techniques, and it would also be of value to determine how the surface coverage of gold with platinum affects hydrogen adsorption and the Tafel parameters for hydrogen evolution and dissolution.

Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author) Pratt & Whitney Aircraft Division United Aircraft Corporation East Hartford, Connecticut		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP
3. REPORT TITLE INVESTIGATION OF MECHANISMS FOR ELECTROCHEMICAL CATALYSIS		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Quarterly Progress Report, November 1, 1966 through January 31, 1967		
5. AUTHOR(S) (Last name, first name, initial) Aylward, John R., and Smith, Stanley W.		
6. REPORT DATE May 1967	7a. TOTAL NO. OF PAGES 16	7b. NO. OF REFS 0
8a. CONTRACT OR GRANT NO. DA 26-043-AMC-02205(E)	8a. ORIGINATOR'S REPORT NUMBER(S) PWA-3051	
8b. PROJECT NO. IC014501A34A00	8b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) ECOM-02205-3	
8c. Task 11		
8d.		
10. AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY U.S. Army Electronics Command Fort Monmouth, New Jersey 07703 AMSEL-KL-PE	
13. ABSTRACT A program is being conducted to investigate the mechanisms of electrocatalysis with respect to the anodic oxidation of selected fuels by novel electrocatalysts in acid electrolyte at temperatures below 150°C and at ambient pressure. Major emphasis has been given to the investigation of the properties of transition metal silicides when surface-doped with platinum, gold, or both. Conflicts had occurred in the data for silicides incorporated on gold and gold-plated current collectors, but investigation during the current quarter indicates that the conflicts resulted from platinum contamination. The study also showed that $TiSi_2$ exhibits some activity for hydrogen and methanol oxidation. The electrochemical behavior of WSi_2 in acid electrolyte was studied and was found to be similar to that of $MoSi_2$. Both of these materials have tetragonal structures. VSi_2 and $TaSi_2$ also have similar electrochemical characteristics and both have hexagonal structures. Experiments with platinum-doped $TiSi_2$ electrodes indicate that relatively large amounts of platinum are required to obtain a catalytic activity which approaches that of an equivalent platinum sheet and that the utilization of the platinum is low. However, gold-platinum co-deposits on $TiSi_2$ exhibit markedly different behavior. The current obtained from the co-deposits as the ratio of gold to platinum was varied shows maxima at 50 and 70 weight percent of gold and a sharp minimum at 55 weight percent of gold. The maxima are higher than the levels of activity obtained with platinum alone.		

DD FORM 1473
1 JAN 64

Security Classification

Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Electrochemical Catalysis		4				
Hydrogen Oxidation		4				
Methanol Oxidation		4				
Silicides		1				
Corrosion		1				

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (corporate author) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- "Qualified requesters may obtain copies of this report from DDC."
- "Foreign announcement and dissemination of this report by DDC is not authorized."
- "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.

DD FORM 1473 (BACK)

Security Classification